

## Perfluoropolyethers.

*Report 2*

*prof. B. Maximov*


*RSC "Applied Chemistry" , S.-Petersburg, Russia, e-mail : boris\_maximov@mail.ru*

The oxidization of perfluoroolefines (hexafluoropropylene, tetrafluoroethylene) in the liquid phase using different initiation methods (UV-radiation or chemical compounds use (fluorine etc.) is the main commercial perfluoropolyethers' obtaining method.

Taking into account this fact we further will discuss only these two directions of perfluoropolyethers' synthesis. In this article you will find a short review of particularities of both methods. Hereinafter the main attention is paid to perfluoropolyethers' synthesis method fluorine initiated and also to the synthesis of perfluoropropylene oxides' derivatives obtained.

### **Photooxidation of Perfluoroolefines in Liquid Phase.**

Hexafluoropropylene photooxidation in condensed phase at  $-60^{\circ}\text{C}$  produces low-molecular compounds only in small quantities, there are mainly  $\text{COF}_2$  and  $\text{CF}_3\text{COF}$  among them, and more than 90% of hexafluoropropylene transforms into viscous mixture of oligomers with the common formula

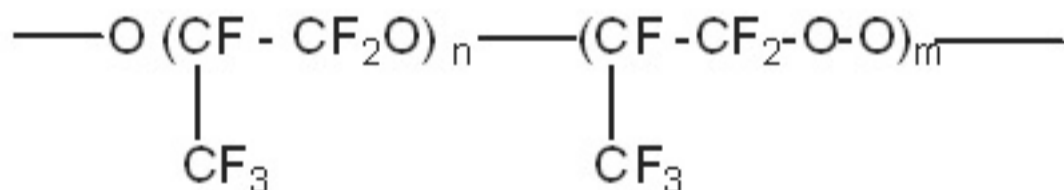

Using NMR  $\text{F}^{19}$  it is stated, that links are connected to each other mainly according "head to tail" type (1). The average polymerization degree (n+m) is 30-40.

The breakdown time of fluoroolefines' oxygen oxidization reaction is not long. If we add a small amount of peroxides there won't be any breakdown time.

Tetrafluoroethylene oxidizes in the inert solvent solution (for example difluorodichloromethane, oxygen saturated (1,2) at atmospheric pressure because of its tendency to polymerize.

At that the main synthesis' products were  $\text{CF}_2\text{O}$ , tetrafluoroethylene and high-molecular viscous compounds - perfluoropolyethylene oxides, their average molecular mass is  $10^4$ - $10^5$ . Their structure is as follows:






At tetrafluoroethylene oxidation the total quantum yield is higher than at

hexafluoropropylene oxidation, but it much depends on reaction's conditions.

During the temperature drop from - 60°C up to +20°C the peroxides' content decreases.

Fluoroolefines photooxidation mechanism is a complicated process, in which three different types of radicals participate: they are perfluoroalkyl ( $R_F^*$ ), perfluoroalkoxil ( $R_FO^*$ ) and perfluoroperoxide ( $R_FOO^*$ ).

Here are most important elemental reactions according to works' data (1,2):

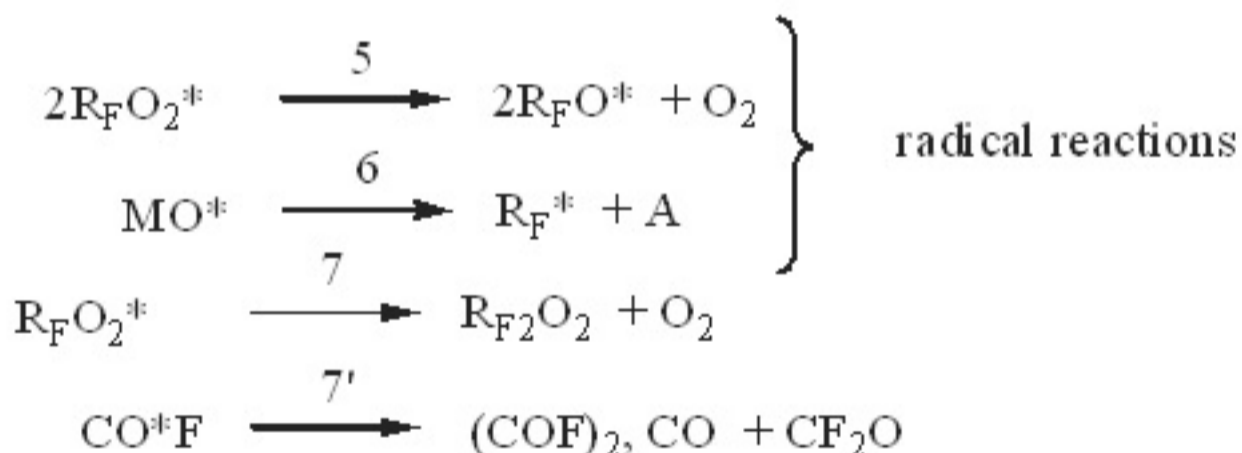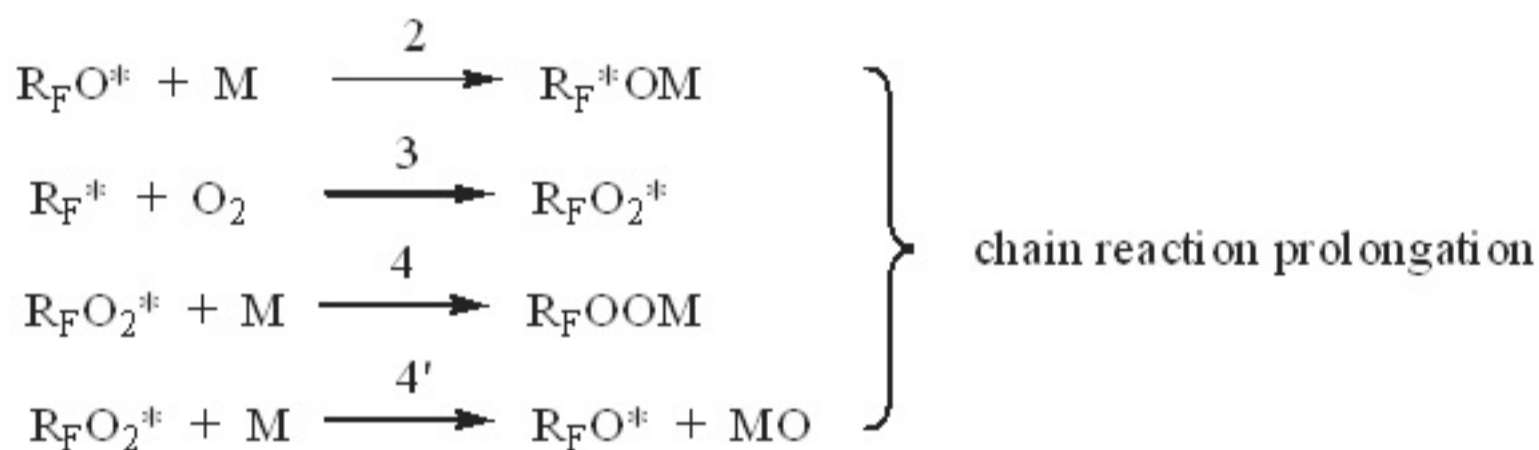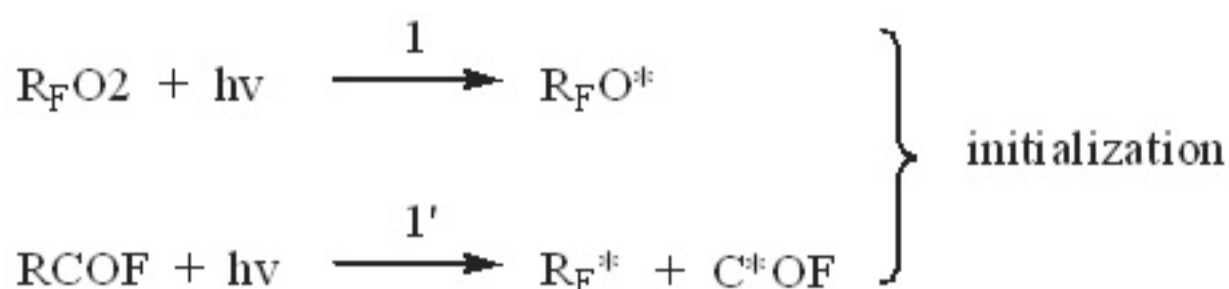

where:  $M=C_2F_4$  or  $C_3F_6$ ;  $R_F=CF_3$ ,  $M$

$A=CF_2O, CF_3COF$

The fluoroolefines oxygen photooxidation reactions' mechanism can be described by the following stages.

### A) Initiation Reaction

The reaction is initiated by UV-light of medium and low pressure lamps which wave length is less than 320nm. Admixtures free fluoroolefines and oxidation products don't absorb light which wave length is more than 200 nm, in consequence of what the reaction breakdown

time is always short, when small amounts of fluorolefine transform into compounds absorbing light such as- CF<sub>3</sub>COF or peroxides. At peroxides' photolysis O-O link opens / is destroyed, at acylfluorides' photolysis C-C link opens. At that free radicals are formed, initiating chain reaction between olefins and oxygen.

### **B) Chain Carrying on Reaction**

Reactions 2,3,4 are stages of chain growth. Out of them reaction 4 may take place in most cases, though other ways are possible too.

### **C) Radicals' Reactions**

It is known, that perfluoro-alkoxyradicals tend to dissociate according to C-C link even at low temperature (4). Therefore the reactions of 5,6 radicals' dissociation take a biggest part at stage of chain propagation. The structure of final polyether is determined by competition of 2-6 reactions.

### **D) Chain Termination Reactions**


As is shown (3) one of possible chain termination reactions is a reaction of two alkoxyradicals 7 recombination. The bigger part of radicals will recombine by reaction 5, forming two radicals, participating in chain propagation.

As we have mentioned before, the main drawbacks of fluorolefines photochemical oxidation are:

- low process productivity
- Complicated apparatus mounting (sealing of quartz lamps)
- low efficiency of UV-radiation source (93% are IR radiation of heat) etc.


Taking this into account the most progressive is the method of radical fluorolefines and oxygen co-polymerization when using chemical compounds able to homolytically dissociate at low temperatures - for example elemental fluorine.

Using NMR F<sup>19</sup> method we determined the structure of perfluoropolyethers on the base of hexafluoropropylene:

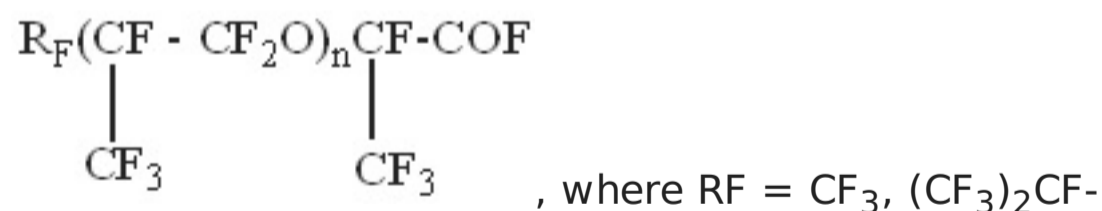

The particular feature of it is that in the structure of the compounds virtually there are no fluoroformate and difluoromethyleneoxide groups, which are imperative at photochemical oxidation.


At using of chemical initiation the hexafluoropropylene and oxygen co-polymerization reactions occur according to the following scheme:

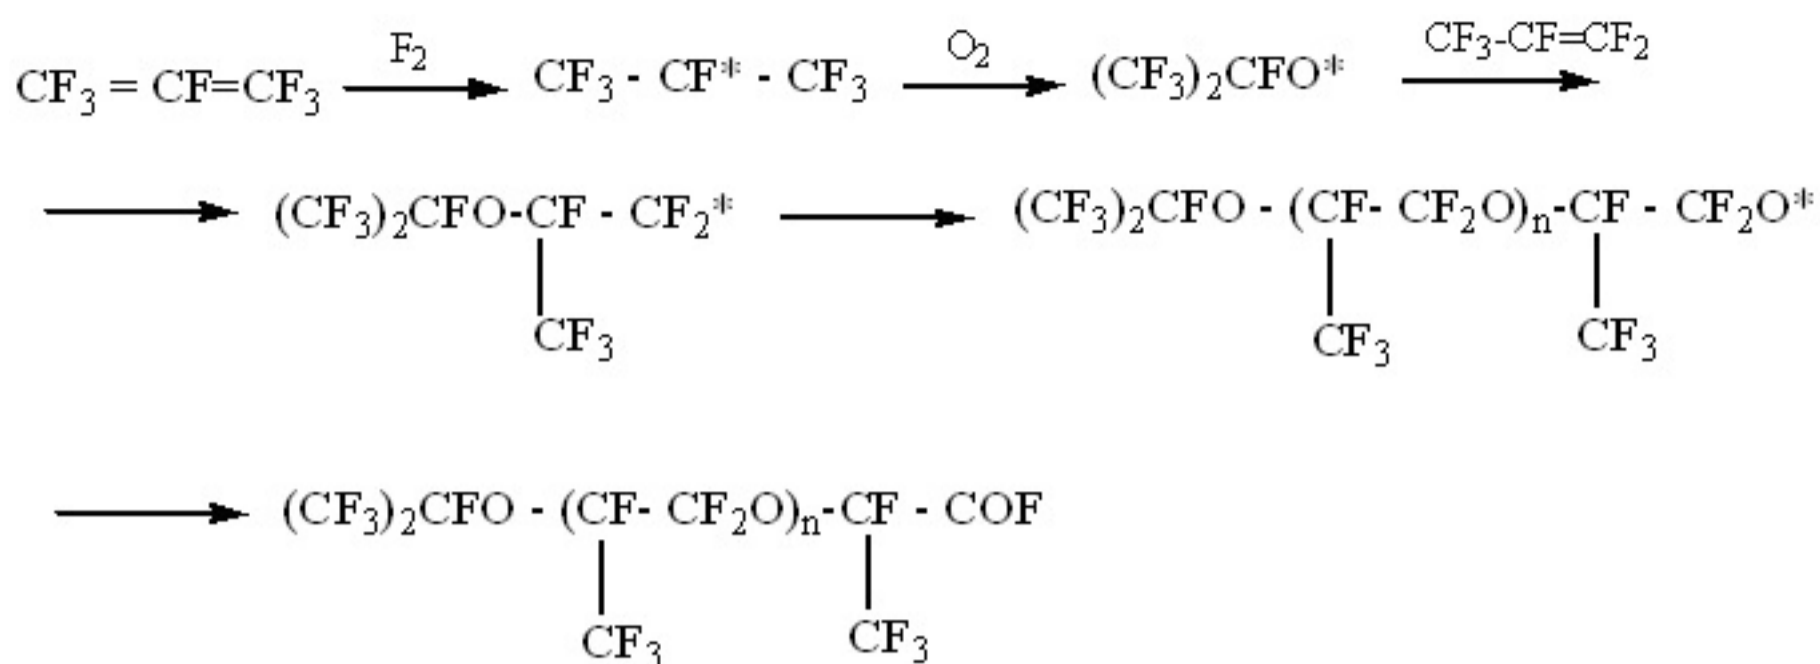

The characteristic property of chemical initiation of hexafluoropropylene and oxygen copolymerization process is the absence of reaction by-products' inhibitory action ( $\text{COF}_2$ ,  $\text{CO}$ ,  $\text{CO}_2$ ,  $\text{CF}_3\text{COF}$  etc.)

Perfluoropropyleneoxides are reaction products, they are colorless viscous liquids ( $n_D^{20} = 1.00-1.01$  and more) with density 1,83-1,92  $\text{g/cm}^3$  and molecular mass 800-10000. Molecular-weight depending of perfluoropolyethers at synthesis temperature changing from -30 to -50  $^{\circ}\text{C}$  is shifting to high-molecular compounds.

Perfluoropolyether acids fluoroanhydrides are functional perfluoropolyethers, obtained at chemical initiation using fluorine,

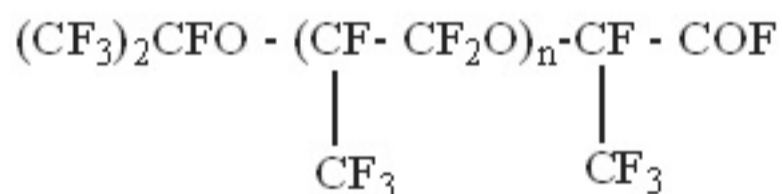

which in the open air slowly hydrolyze forming perfluoropolyether acids in hydrate form (jelly-like mass).

Fluoroanhydrides are rather reactive compounds and they are used for synthesis of different useful compounds.

## References

1. Sianesi D., Am. Chem. Soc., Polymer-Preprints, 1971, v. 12, #1, p. 411
2. Sianesi D., Pasetti A. at all, III European Symposium on Fluorine Chemistry, Aix-Eu-Provens, Sept. 1970
3. Hovard I.A., Ingold K., Can. J. Chem., 1965, v. 43, 2729